

KEVLAR®



KEVLAR® engineered elastomer with Neoprene GRT

Merge 1F735

Test compound formulation and properties:

Neoprene GRT		100	90.8	84.5	69.2
Engineered elastomer 1F735		0	12	20	40
Magnesia (Maglite D)		4	4	4	4
N772 carbon black		58	58	58	58
Rapeseed oil		10	10	10	10
Stearic acid		2	2	2	2
Octylated diphenylamine (Octamine)		2	2	2	2
Zinc oxide		5	5	5	5

KEVLAR® Engineered Elastomer content	pphr	0	12	20	40
KEVLAR® pulp content	pphr	0	2.8	4.6	9.2

Mooney Viscosity at 100°C

ML 1 + 4	units	49.1	50.8	55.4	69.7
----------	-------	------	------	------	------

Mooney Scorch MS at 121°C

Time to + 5 units raise	min	42.1	38.5	41.5	41.1
Time to + 10 units raise	min	48.5	46.1	48.2	47.2
Minimum	min	15.7	18.7	21.3	26.3

ODR 160°C, 30 min, 3° arc

M _L	dN/m	6.4	7.3	9.5	13.9
t _{s2}	min	3.28	3.14	3.07	2.77
t ₉₀	min	19.1	21.8	22.5	23.4
M _H	dN/m	75.9	86.2	90.9	111.3

Vulcanizate properties measured on 2 mm sheet


Cure time	min	20	25	25	25
Hardness	°IRHD	68	77	79	88
	°Shore A	67	78	81	89

Machine and cross direction:

		MD	XD	MD	XD	MD	XD	MD	XD
Tensile strength	MPa	19.6	18.5	18.5	15.3	18.2	14.1	16.6	13.9
Modulus at 10%	MPa	0.6	0.6	1.2	1.0	4.7	1.3	9.4	2.3
Modulus at 15%	MPa	0.8	0.7	2.1	1.4	7.4	1.8	12.2	3.2
Modulus at 25%	MPa	1.1	1.0	4.6	2.1	10.1	2.7	14.3	4.8
Modulus at 30%	MPa	1.2	1.2	5.7	2.3	10.5	3.0	14.9	5.6
Modulus at 50%	MPa	1.8	1.7	7.3	3.7	10.6	4.2		8.1
Modulus at 100%	MPa	3.7	3.4	8.1	5.7	11.6	6.3		11.1
Modulus at 200%	MPa	10.2	9.3	13.1	11.5	13.4	11.7		
Elongation at break	%	347	400	301	368	248	337	31	137
Tear ISO 34C	kN/m	46.1	43.5	56.7	55.2	63.1	60.8	83.9	71.6
Tear ISO 34B	kN/m	44.5	41.7	46.1	53.9	49.1	52.5	52.9	74.1


This information represents our current knowledge on the subject. It is offered solely to provide possible suggestions for your own experimentation. It is not intended, however, to substitute for any testing you may need to conduct to determine for yourself the suitability of our products for your particular purposes. This information is subject to revision as new knowledge and experience becomes available. Since we cannot anticipate all variations in actual end-use conditions, DuPont makes no warranties and assumes no liability in connection with any use of this information. Nothing in this publication is to be considered as a license to operate under or a recommendation to infringe any patent right.

Effect of KEVLAR® Engineered Elastomer Content on Processing

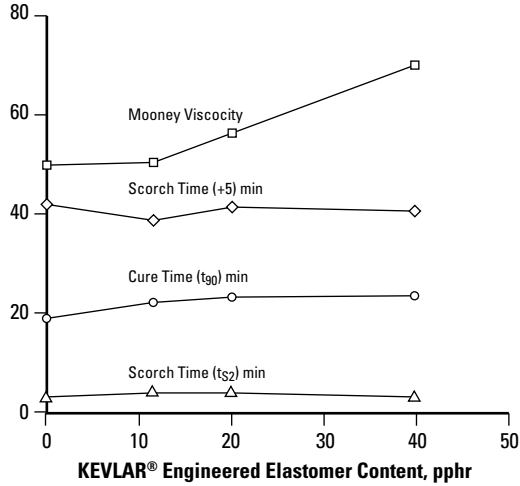


- Engineered elastomer merge 1F735 contains:
 - 23 weight percent reinforcement
 - 77 weight percent Neoprene GRT
- Specific Gravity is 1.28
- “Nugget” shape product form
- Packaged in 15 kilogram kraft bags with a low melt (<100°C) EVA liner

Effect of KEVLAR® Engineered Elastomer Content on Tensile Strength and Modulus

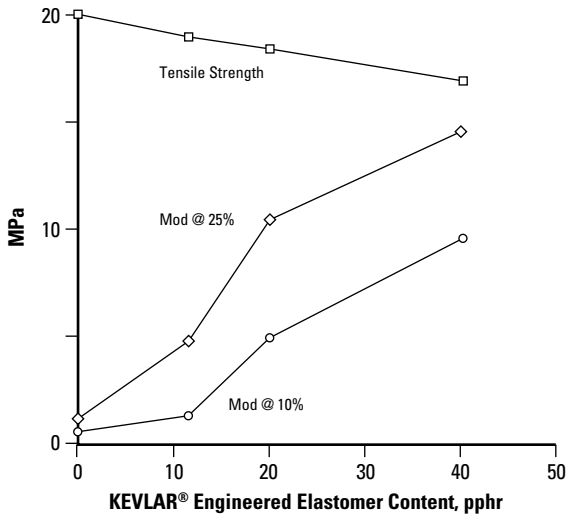

Effect of KEVLAR® Engineered Elastomer Content on Tear Strength

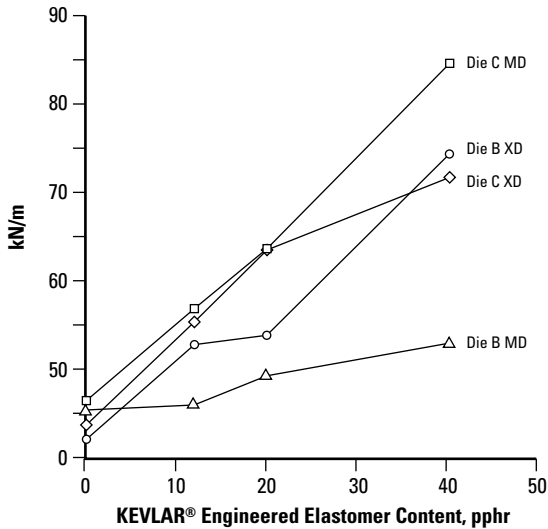

DuPont Advanced Fibers Systems
 Customer Inquiry Center
 5401 Jefferson Davis Highway
 Richmond, VA 23234
 Tel: (800) 453-8527
 (804) 383-4400
 Fax: (800) 787-7086
 (804) 383-4132
 E-Mail: afscdt@usa.dupont.com
Web Address: www.kevlar.com

